



Cite as

Nano-Micro Lett.
(2021) 13:189Received: 19 May 2021
Accepted: 12 July 2021
© The Author(s) 2021


Surface Oxygen Injection in Tin Disulfide Nanosheets for Efficient CO₂ Electroreduction to Formate and Syngas

Tao Chen^{1,2}, Tong Liu¹, Tao Ding¹, Beibei Pang¹, Lan Wang^{1,2}, Xiaokang Liu¹, Xinyi Shen¹, Sicong Wang¹, Dan Wu¹, Dong Liu¹, Linlin Cao¹, Qiquan Luo³, Wei Zhang^{1,4} ✉, Wenkun Zhu² ✉, Tao Yao¹ ✉

HIGHLIGHTS

- A surface oxygen-injection strategy is proposed to synergistically modulate the electronic structure of the SnS₂ nanosheets, thereby regulating the oxophilicity of the catalyst surface.
- The surface oxygen doping facilitates the CO₂ activation and enhances the affinity for HCOO* species.
- The oxygen-injection SnS₂ nanosheets exhibit a remarkable Faradaic efficiency of 91.6% for carbonaceous products with a current density of 24.1 mA cm⁻² at -0.9 V vs RHE.

ABSTRACT Surface chemistry modification represents a promising strategy to tailor the adsorption and activation of reaction intermediates for enhancing activity. Herein, we designed a surface oxygen-injection strategy to tune the electronic structure of SnS₂ nanosheets, which showed effectively enhanced electrocatalytic activity and selectivity of CO₂ reduction to formate and syngas (CO and H₂). The oxygen-injection SnS₂ nanosheets exhibit a remarkable Faradaic efficiency of 91.6% for carbonaceous products with a current density of 24.1 mA cm⁻² at -0.9 V vs RHE, including 83.2% for formate production and 16.5% for syngas with the CO/H₂ ratio of 1:1. By *operando* X-ray absorption spectroscopy, we unravel the in situ surface oxygen doping into the matrix during reaction, thereby optimizing the Sn local electronic states. *Operando* synchrotron radiation infrared spectroscopy along with theoretical calculations further reveals that the surface oxygen doping facilitated the CO₂ activation and enhanced the affinity for HCOO* species. This result demonstrates the potential strategy of surface oxygen injection for the rational design of advanced catalysts for CO₂ electroreduction.

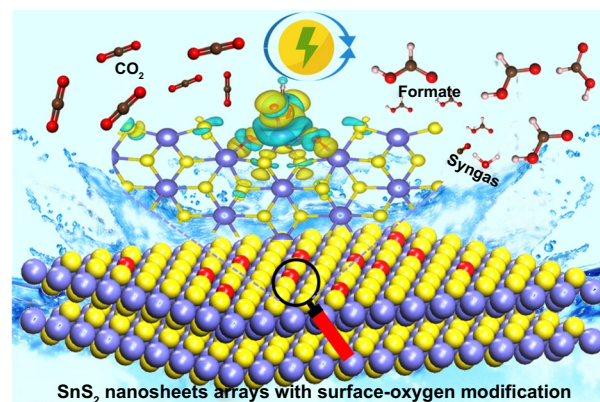

KEYWORDS Oxygen injection; Tin disulfide; CO₂ electroreduction; Formate; Syngas

Tao Chen and Tong Liu contributed equally to this work.

✉ Wei Zhang, zwei2319@mail.ustc.edu.cn; Wenkun Zhu, zhuwenkun@swust.edu.cn; Tao Yao, yaot@ustc.edu.cn

¹ National Synchrotron Radiation Laboratory, University of Science and Technology of China, Hefei 230029, People's Republic of China

² State Key Laboratory of Environmentally Friendly Energy Materials, School of National Defense Science and Technology, Southwest University of Science and Technology, Mianyang 621010, People's Republic of China

³ Institutes of Physical Science and Information Technology, Anhui University, Hefei 230601, People's Republic of China

⁴ School of Materials, Sun Yat-Sen University, Guangzhou 510275, People's Republic of China

Published online: 06 September 2021



SHANGHAI JIAO TONG UNIVERSITY PRESS

Springer

1 Introduction

Electroreduction of carbon dioxide (CO₂RR) into high-value fuels and feedstocks offers a compelling pathway not only to meet the increasing energy demand, but also to alleviate the environmental crisis caused by CO₂ emissions [1–3]. According to the gross-margin model, formate is considered to be one of the most economically feasible products in the CO₂RR, which can be widely used as an important raw material in the chemical and pharmaceutical industries, as well as a potential hydrogen carrier and the liquid fuel for proton-exchange membrane fuel cell [4–6]. Up to now, various metal-based electrocatalysts, such as Pd, In, Hg, Pb, Cd, and Sn, have been exploited to achieve the CO₂ electroreduction to formate [7–13]. Among these electrocatalysts, Sn-based materials have attracted considerable attention due to their advantages of earth abundance, non-toxicity, and low cost. Unfortunately, the catalytic performance of most Sn-based materials is still limited by the high energy barrier for CO₂ activation, which is usually attributed to the poor stabilization of CO₂*⁻ intermediates [14–18]. To this end, it is of great significance to develop an efficient and durable Sn-based catalysts for the CO₂ electroreduction to formate.

Given that the CO₂ molecule activation is closely related to the number and inherent activity of active sites, many effective strategies have been employed to tailor the active sites of electrocatalysts for enhancing the efficiency of the CO₂ electroreduction to formate [19–21]. The surface chemistry modification, as a powerful strategy, has attracted great interest in adjusting electronic properties of active sites to target intermediate adsorption energy as well as harvest high selectivity [22–25]. For example, Xie et al. developed a general amino acid modification approach on Cu electrodes for the selective electroreduction of CO₂ toward hydrocarbons [26]. Previous theoretical calculations have confirmed that the *OCHO binding energy is closely associated with the oxophilicity of the catalyst surface, which can be achieved by modifying the surface of the electrocatalyst with oxygen atom [27]. For instance, Gao et al. reported a phenomenon that partially oxidized atomic cobalt layers effectively adjusted the electronic structure, promoted the activation of CO₂, and stabilized the relevant key intermediates, thereby enhancing the efficiency of the CO₂ electroreduction to liquid fuel [28]. As another example, Won et al. prepared hierarchical Sn dendrites and found that the

natural oxygen content is closely related to the stability of CO₂*⁻ intermediates and the selectivity of formate [29]. To improve the catalytic performance of Sn-based materials, oxygen modification is a promising strategy to regulate the surface oxophilicity of the catalysts and further manipulate their electronic structure. In fact, most of the catalysts with surface chemical modification have undergone structural evolution of the active phase under operation conditions, leading to deviations in the understanding the nature of the active site. Therefore, monitoring the structural evolution of Sn-based catalysts with surface oxygen modification under realistic working conditions is crucial for understanding the nature of the active phase and the rational design of targeted CO₂RR catalysts.

Herein, the SnS₂ nanosheets arrays on the carbon paper with surface oxygen modification were rationally designed under the guidance of density function theory (DFT) to effectively electroreduce CO₂ into formate and syngas (CO and H₂). The introduction of oxygen into the surface of SnS₂ nanosheets achieved the exposure of Sn active sites and optimal Sn electronic states, thereby enhancing the adsorption and activation of CO₂. Specifically, the SnS₂ nanosheets with surface oxygen modification exhibit a remarkable Faradaic efficiency of 91.6% for carbonaceous products at -0.9 V vs RHE, including 83.2% for formate production and 16.5% for syngas with the CO/H₂ ratio of 1:1. Operando X-ray absorption spectroscopy unravels that the in situ surface oxygen doping into the matrix under working conditions effectively changes the local electronic state of Sn, thereby providing an optimized electronic structure to improve CO₂RR performance. In addition, operando synchrotron radiation infrared spectroscopy and DFT calculations further confirm that the local electronic state of Sn is manipulated through surface oxygen modification, thereby promoting the CO₂ activation and enhancing the affinity for HCOO* species.

2 Experimental Section

The experimental details are provided in Supporting Information (SI). This section briefly summarizes the synthesis measurements.

In a typical synthesis of SnS_{2-x}O_x/CC, 5 mmol of SnCl₄·5H₂O and 15 mmol of thioacetamide were dissolved in 40 mL of deionized water. The mixture and carbon paper (2×2) were then transferred into a Teflon-lined

stainless-steel autoclave, followed by being heated to 190 °C for 8 h. After the mixture was cooled down naturally to room temperature, the SnS₂/CC was washed by water three times and ethanol twice to remove any possible ions, followed by being dried under vacuum at 60 °C for 12 h. The SnS_{2-x}O_x/CC was prepared by placing the SnS₂/CC in the muffle furnace that had been heated at 300 °C for several minutes.

3 Results and Discussion

3.1 Preparation and Characterization of SnS_{2-x}O_x/CC

At first, to gain insight into the effect of surface oxygen-injection engineering on electronic properties of SnS₂ nanosheets, we conducted DFT calculations by using the SnS₂ slab with/without oxygen injection as the models (Fig. 1a, b). Compared with the pristine SnS₂, the surface oxygen injection leads to a new additional state near the Fermi level (Fig. 1c, d), which is beneficial to manipulate the local electronic structure of Sn and expose the active site of Sn at the edges. Notably, O 2*p* states also contributed the unoccupied part of these levels, making them serve as the highly catalytically active sites. Furthermore, the electronic localization functions (ELF) exhibit that the charge density is mainly derived from the S atoms for both the SnS₂ with/without oxygen injection (Fig. S1). Owing to the introduction of oxygen atoms, the electron density of the whole system has undergone distinctly change, further indicating surface oxygen injection effectively tailors the local electronic structure of Sn.

Then, the SnS₂ nanosheets arrays with partially oxidized surface on the carbon paper (denoted as SnS_{2-x}O_x/CC) were prepared, as schematically illustrated in Fig. 2a. Specifically, the pristine SnS₂ nanosheets arrays were directly grown on the carbon paper by a simple hydrothermal method. Afterward, the SnS_{2-x}O_x/CC was further synthesized by the low-temperature calcination of the as-prepared SnS₂/CC under the air atmosphere. The morphology of the SnS_{2-x}O_x/CC was characterized by scanning electron microscopy (SEM) and transmission electron microscopy (TEM). As shown in Fig. 2b, the final products present a hierarchical nanosheets arrays composed of SnS_{2-x}O_x nanosheets and flexible carbon paper. The TEM images of the SnS₂ and SnS_{2-x}O_x took the nanosheet morphology (Figs. 2c and S2a), whereas the SnS₂ nanosheets were completely oxidized into SnO₂

nanoplatelets (Fig. S3). The high-resolution transmission electron microscopy (HRTEM) image in Fig. 2d shows that the SnS_{2-x}O_x lattice fringes with an interplanar distance of 0.32 nm indexed to the (002) facets of SnS₂, confirming the as-obtained SnS_{2-x}O_x nanosheets retain its pristine crystal structure (Fig. S2b, c) [30]. Besides, there is an obvious circle of amorphous layer at the edge of the SnS_{2-x}O_x nanosheet, which is attributed to the partial oxidation on the surface of the SnS₂ nanosheet. In addition, the homologous fast Fourier transform (FFT) pattern indicates the SnS₂ phase recorded from [002] orientation (inset in Fig. 2e). The element of O was uniformly distributed on the whole SnS_{2-x}O_x nanosheet which can be further confirmed by the high-angle annular dark-field energy-dispersive X-ray spectroscopy (HAADF-EDS) elemental mapping and EDS spectrum (Figs. 2f and S4).

To further investigate the phase composition and electronic structure of the SnS_{2-x}O_x/CC, we performed X-ray diffraction (XRD) and X-ray photoelectron spectroscopy (XPS) measurement. As evidenced by the XRD patterns in Fig. S5, the SnS₂/CC and SnS_{2-x}O_x/CC exhibited the diffraction peaks at 30.74°, 32.09°, and 44.98°, which were indexed to the (200), (101), and (211) planes of hexagonal SnS₂ (JCPDS No. 23-0677) [31]. Remarkably, no additional peaks corresponding to the phases of SnO₂ could be found, indicating that the surface oxygen injection did not change the crystalline phase of SnS₂. We further carried out the XPS measurements to clarify the form of O existing in SnS_{2-x}O_x/CC. As disclosed by XPS survey spectra, a weak signal of O was recorded in SnS_{2-x}O_x/CC, further confirming successful introduction of O (Figs. S6 and S7). In addition, the peaks at 495.3 and 486.8 eV were attributed to Sn 3*d*_{3/2} and Sn 3*d*_{5/2} of SnS_{2-x}O_x/CC, respectively (Fig. S8) [32]. Compared with the SnS₂/CC, the Sn 3*d*_{3/2} and 3*d*_{5/2} peaks for SnS_{2-x}O_x/CC shifted to higher binding energies, due to the larger electronegativity of O than that of S.

The surface-sensitive synchrotron radiation soft X-ray absorption structure (XAS) was further employed to investigate the changes in the local electronic structure of SnS₂ caused by surface oxygen-injection engineering. As shown in Fig. S9, O *K*-edge XAS spectra for SnS_{2-x}O_x/CC and pure SnO₂/CC displayed similar shapes, implying SnO₂ species were formed on the surface of SnS_{2-x}O_x/CC, further confirming the surface oxygen injection successfully replaced the S atoms. In addition, S *L*-edge XAS spectra exhibited the two characteristic peaks located at 163.3 eV (S-Sn π*

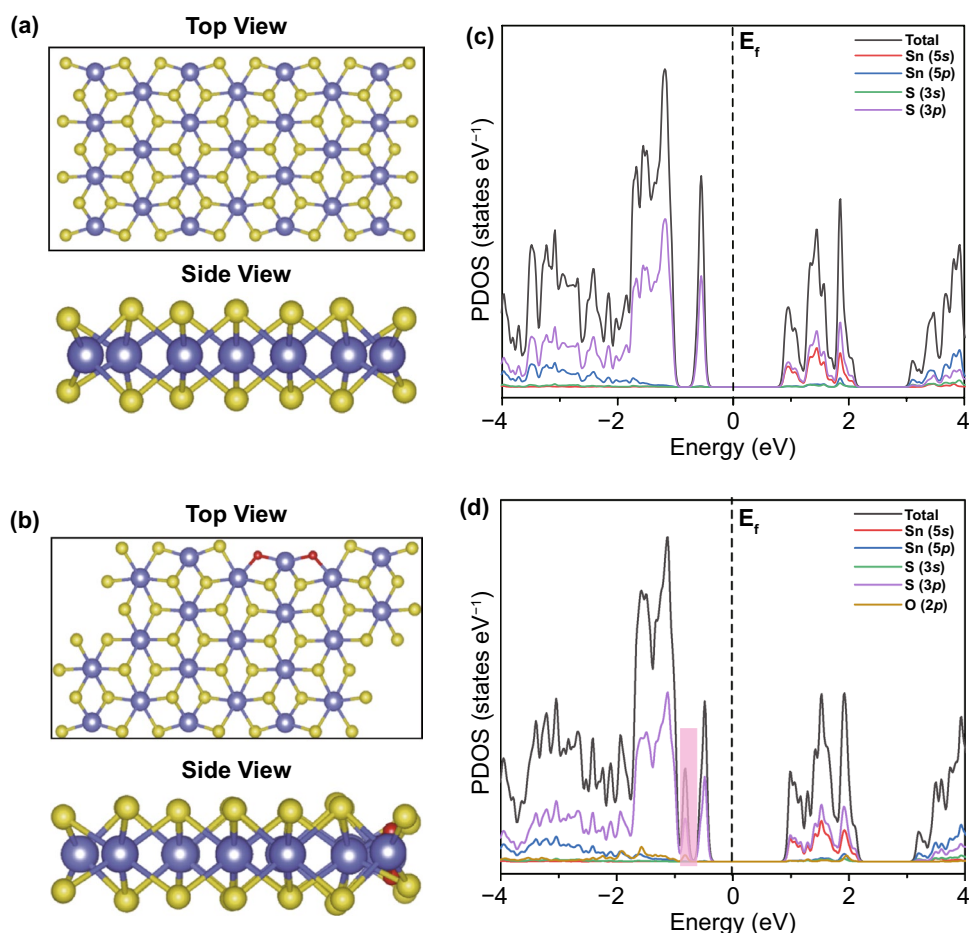


Fig. 1 Top view and side view of the model for **a** pristine SnS_2 and **b** $\text{SnS}_{2-x}\text{O}_x$. Calculated DOS of **c** SnS_2 and **d** $\text{SnS}_{2-x}\text{O}_x$ slabs

peak) and 166.6 eV (S-Sn σ^* peak) observed in pure SnS_2/CC and the $\text{SnS}_{2-x}\text{O}_x/\text{CC}$ (Fig. S10). Compared with pristine SnS_2/CC , the relative strength of S-Sn for $\text{SnS}_{2-x}\text{O}_x/\text{CC}$ was slightly reduced, which was attributed to the substitution of partial S atoms on the surface of $\text{SnS}_{2-x}\text{O}_x/\text{CC}$ by O atoms. Meanwhile, the X-ray absorption near-edge structure (XANES) measurement was employed to further investigate the effect of surface oxygen injection. Compared with pristine SnS_2/CC , the white line peak of the $\text{SnS}_{2-x}\text{O}_x/\text{CC}$ shifted to the high- E region, due to the electronegativity of O being greater than that of S, in consistent with the results of Sn 3d XPS spectrum (Fig. S11). Given that the white line peak of Sn K -edge intensity originating from the transition of the 1 s to 5 p orbital, the increase in the white line peak intensity after surface oxygen injection indicates the increases in the

possibility of electron transition from the 1 s -5 p orbital. The above results reveal the surface oxygen injection effectively manipulates the local electronic structure of Sn.

Furthermore, the Fourier transform (FT) k^2 -weighted extended XAFS (EXAFS) spectrum of the Sn K -edge was employed to further reveal the effect of surface oxygen injection on the local electronic structure of Sn at the atomic level. Considering the surface oxygen injection into the SnS_2 nanosheets, we performed out least-squares EXAFS curve fitting analysis for Sn by considering two backscattering paths, including Sn-S and Sn-O. Compared with the SnS_2/CC , the Sn K -edge FT-EXAFS curve for $\text{SnS}_{2-x}\text{O}_x/\text{CC}$ presented a new peak at 1.49 Å, which is ascribed to the Sn-O coordination (Fig. 2a) [33]. By quantitative EXAFS curve fitting analysis, the coordination number of Sn-S for

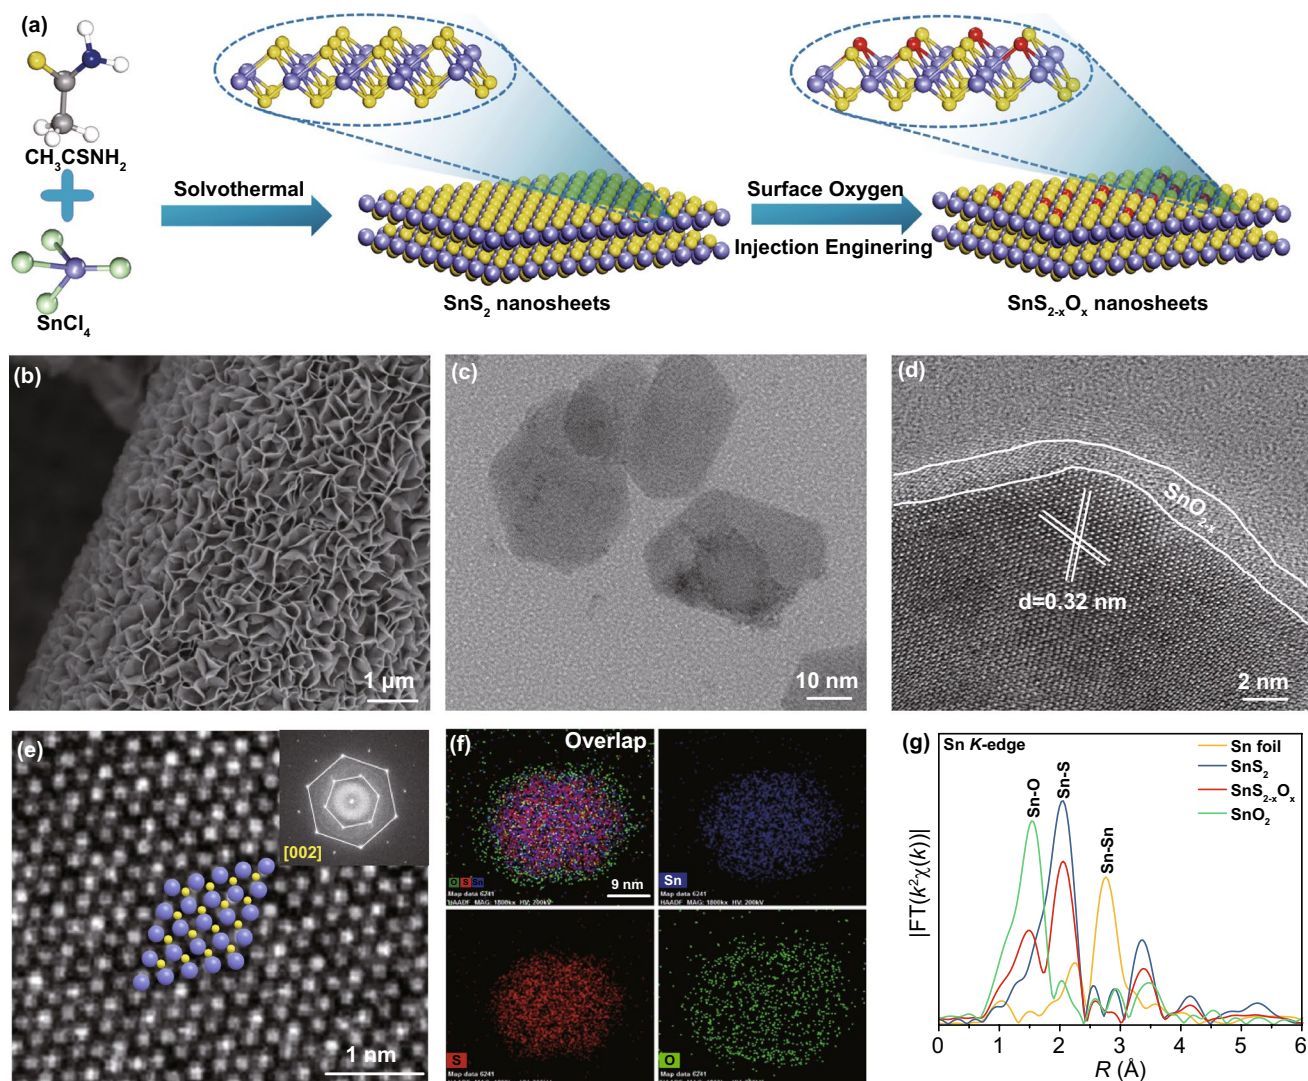


Fig. 2 **a** Schematic illustration of the manufacture of $\text{SnS}_{2-x}\text{O}_x$ nanosheets. **b** SEM image of $\text{SnS}_{2-x}\text{O}_x/\text{CC}$. **c** TEM image of $\text{SnS}_{2-x}\text{O}_x$ nanosheets. **d**, **e** HRTEM image and the homologous FFT pattern of $\text{SnS}_{2-x}\text{O}_x$ nanosheets (inset in **e**). **f** HAADF-STEM and STEM-EDX elemental mapping images of an individual $\text{SnS}_{2-x}\text{O}_x$ nanosheet. **g** Fourier transform spectra of Sn *K*-edge for Sn foil, SnS_2 , $\text{SnS}_{2-x}\text{O}_x$, and SnO_2 from EXAFS

$\text{SnS}_{2-x}\text{O}_x/\text{CC}$ is confirmed to be 4.3, smaller than that of pristine SnS_2/CC (6.0), and the coordination number of Sn–O is verified to be 2.1, further confirming surface oxygen injection successfully replaced the S atoms (Table S1 and Fig. S12). Moreover, the wavelet transform (WT) of Sn *K*-edge EXAFS oscillations exhibited the intensity maxima at 4.3 \AA^{-1} and around 8.2 \AA^{-1} of $\text{SnS}_{2-x}\text{O}_x/\text{CC}$, which associate with Sn–O and Sn–S contributions, respectively (Fig. S13). Taken together, the successful injection of surface oxygen effectively manipulated the local electronic structure of SnS_2 .

3.2 Electrocatalytic CO_2RR Performances of the $\text{SnS}_{2-x}\text{O}_x/\text{CC}$

Surface oxygen-injection engineering provides a potential prospect for enhancing the CO_2 electroreduction. The electrocatalytic CO_2 reduction activities of the three Sn-based catalysts were evaluated using a three-electrode H-cell in CO_2 -saturated 0.5 M KHCO_3 . The linear sweep voltammetric (LSV) curves in Fig. S14 revealed that the $\text{SnS}_{2-x}\text{O}_x$ nanosheets exhibited higher current density than that of pristine SnS_2 nanosheets, confirming the injection

of oxygen effectively enhanced the electrocatalytic activity of SnS₂/CC. Particularly, the geometrical current density of SnS_{2-x}O_x/CC achieved 19.68 mA cm⁻², which was 2.7 times higher than that of pristine SnS₂/CC at overpotential of -0.8 V vs RHE (Fig. 2a). For these three Sn-based catalysts, H₂, CO, and formate were the main catalytic products, which are quantified by online gas chromatography and ¹H NMR analysis (Fig. S15). Figure 2b exhibits partial current density for carbonaceous products (CO and formate), respectively. At all applied potentials, the SnS_{2-x}O_x/CC presented the largest current density among the three electrocatalysts, demonstrating the high activity for CO₂ electroreduction. As shown in Fig. 2c, the SnS_{2-x}O_x/CC displayed the highest Faradaic efficiency (FE) for carbonaceous products among the three electrocatalysts, while the pristine SnS₂/CC exhibited the lowest FE value. At -0.9 V vs RHE, the SnS_{2-x}O_x/CC exhibited the FE of 91.8% for carbonaceous products, including the FE of 83.5% for formate production and the FE of 16.5% for syngas with the H₂/CO ratio of 1:1. It is worth noting that such syngas ratio is optimal for multiple chemical synthesis (e.g., Fischer-Tropsch synthesis, fermentation and alcohol synthesis, and hydroformylation processes). Furthermore, the as-prepared SnS_{2-x}O_x/CC displayed an excellent durability for 10-h potentiostatic test with the less than 3% decay in current density, together with the FE for formate and CO keeping steady at -0.9 V vs RHE (Fig. 2d). The above results demonstrate that the SnS_{2-x}O_x/CC represents a promising catalyst for persistently producing formate and syngas toward CO₂RR.

Inspired by surface oxygen injection to improve the CO₂ electroreduction performance of SnS₂/CC, we studied the microscopic reaction kinetics of the pristine SnS₂/CC and SnS_{2-x}O_x/CC. Based on cyclic voltammogram measurements at different scan rates, the double-layer capacitance (*C*_{dl}) value increased from 3.27 mF cm⁻² of the pristine SnS₂/CC to 3.75 mF cm⁻² of the SnS_{2-x}O_x/CC, indicating that surface oxygen injection effectively increases the electrochemical active surface area (ECSA) of the electrocatalysts (Figs. S16 and S17). Given that the ECSA of the electrocatalysts is positively correlated with the active sites, we have reason to believe that the surface oxygen modification effectively exposes the active site of Sn. The Tafel plots were further employed to verify the rate-limiting step of the Sn-based catalysts in the CO₂RR process. The Tafel slopes of the Sn-based catalysts were all close to 118 mV dec⁻¹,

demonstrating that the activation of CO₂ served as the rate-limiting step (Fig. S18) [34,35]. In addition, the Nyquist plots were used to confirm the facilitated electron transfer process [36]. The SnS_{2-x}O_x/CC displayed the charge transfer resistance (*R*_{CT}) of 12.1 Ω, which was smaller than that (15.8 Ω) of SnS₂/CC (Fig. S19). Therefore, surface oxygen injection effectively accelerates the charge transfer process of SnS₂/CC during the CO₂RR (Fig. 3).

3.3 Operando X-ray Absorption Spectroscopy Study

Given that the bulk phase stability of transition metal chalcogenides with heat treatment is destroyed, the bulk phase is in a relatively unstable state [37]. Based on the equilibrium theory of crystalline chemistry, the catalyst in the electrolyte driven by both energetical and kinetical force will tend to freely optimize the structure of the entire bulk, so that the bulk tends to a relatively stable state [38–41]. Therefore, we employed *operando* XAFS measurements to monitor the structural evolutions of the SnS_{2-x}O_x/CC under realistic working conditions. Figure 4a shows the *operando* Sn *K*-edge XANES spectra at different applied potentials, along with the data for Sn foil, SnS₂, and SnO₂ as references. When cathodic potentials were applied, the absorption edge of Sn *K*-edge XANES spectra shifted toward low-*E* side compared to the case of the open-circuit condition, indicating the decrease in the Sn valence state during CO₂RR process. Furthermore, when a cathodic potential of -0.9 V versus RHE was applied, the white line peak intensity was significantly increased in relation to the case (-0.4 V versus RHE), indicating more 5*p* electrons participate in the reaction. After the reaction, the white line peak approximately returned to the state (-0.4 V versus RHE), further confirming that the SnS_{2-x}O_x/CC catalyst undergone in situ reconstruction during the reaction and tended to form a relatively stable state.

Furthermore, the EXAFS was further employed to reveal the atomic reconstruction of the SnS_{2-x}O_x/CC catalyst under working conditions (Figs. 4b and S20). At first sight, the Fourier transform curves of SnS_{2-x}O_x/CC displayed a significantly dampening in the Sn-S coordination peak and a heightening in the Sn-nonmetallic coordination peak under working condition. Specifically, at the applied potential of -0.4 V versus RHE before the occurrence of CO₂RR, the

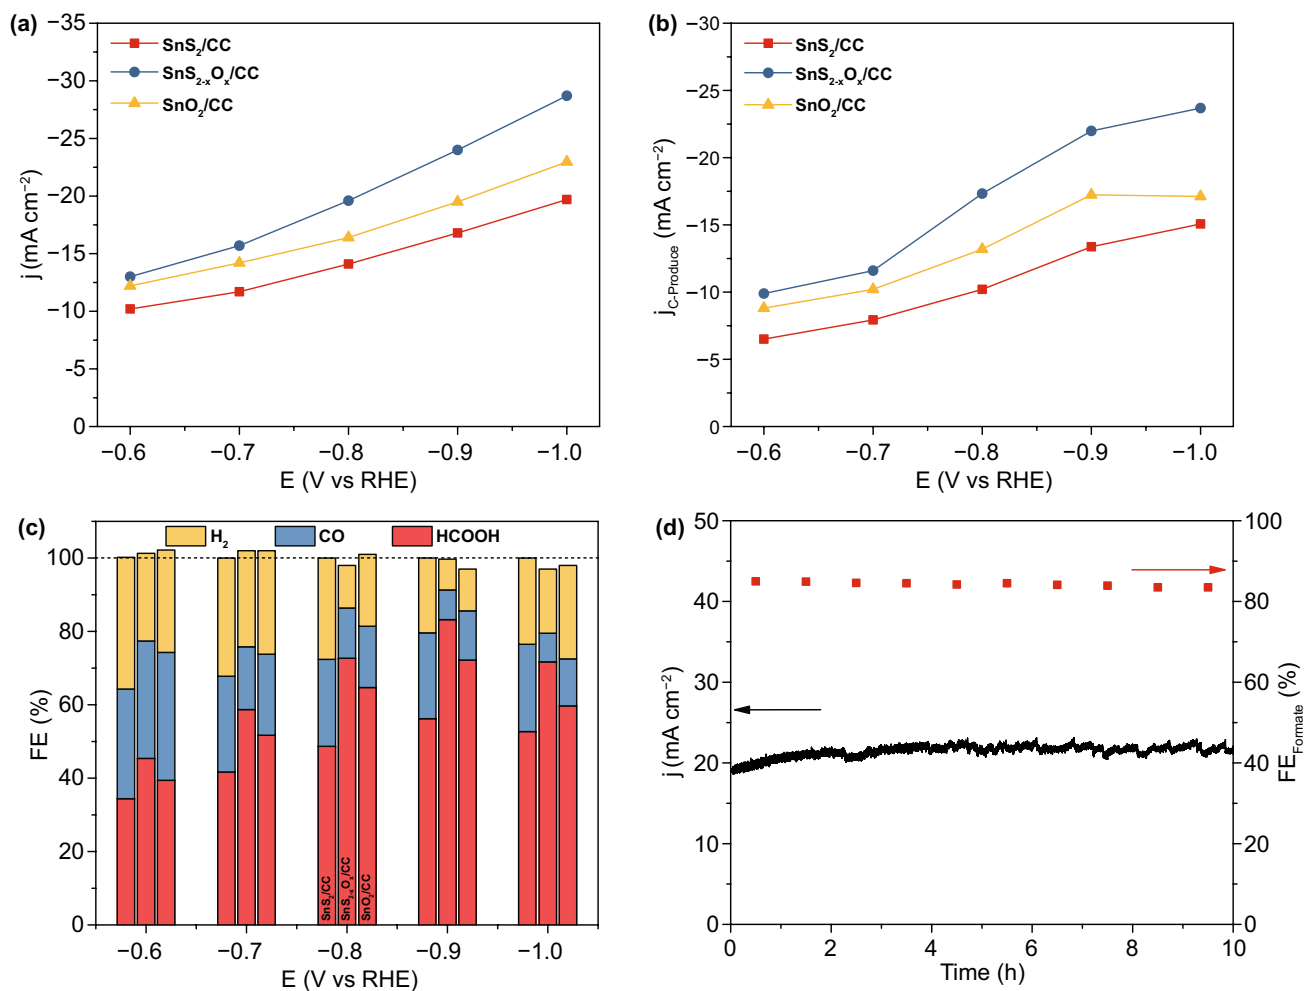


Fig. 3 **a** Geometrical current densities over SnS₂/CC, SnS_{2-x}O_x/CC, and SnO₂/CC. **b** Current densities for carbonaceous product (C-product) over SnS₂/CC, SnS_{2-x}O_x/CC, and SnO₂/CC. **c** Faradaic efficiencies for formate, H₂, and CO production over SnS₂/CC, SnS_{2-x}O_x/CC, and SnO₂/CC. **d** Plot of geometrical current density (j) and Faradaic efficiencies for C-product versus time over the SnS_{2-x}O_x/CC at a constant potential of -0.9 V vs RHE

EXAFS fitting results showed that the Sn–O coordination number increased from 2.5 to 3.6, which may be ascribed to the further doping of surface oxygen into the SnS₂ lattice during the reaction. To further verify the above conjecture, we performed XRD on the SnS_{2-x}O_x/CC after reaction. As expected, the intensity of the diffraction peaks of SnS₂ was significantly reduced after the reaction, and the characteristic peak of SnO₂ appeared in the SnS_{2-x}O_x/CC after reaction (Fig. S21). Moreover, at the potential of -0.9 V versus RHE during CO₂RR, Sn–O coordination number arose

from 3.6 to 4.2 and the Sn–S coordination number remained unchanged, which may be attributed to the adsorption of the reaction intermediate species. When the cathode potential was removed, the Sn–O coordination number recovered to the state at -0.4 V, while the coordination number of Sn–S remained unchanged (Table S2). The above results indicated that the SnS_{2-x}O_x/CC had undergone dynamic surface reconstruction and surface oxygen doping plays a critical role under reaction conditions.



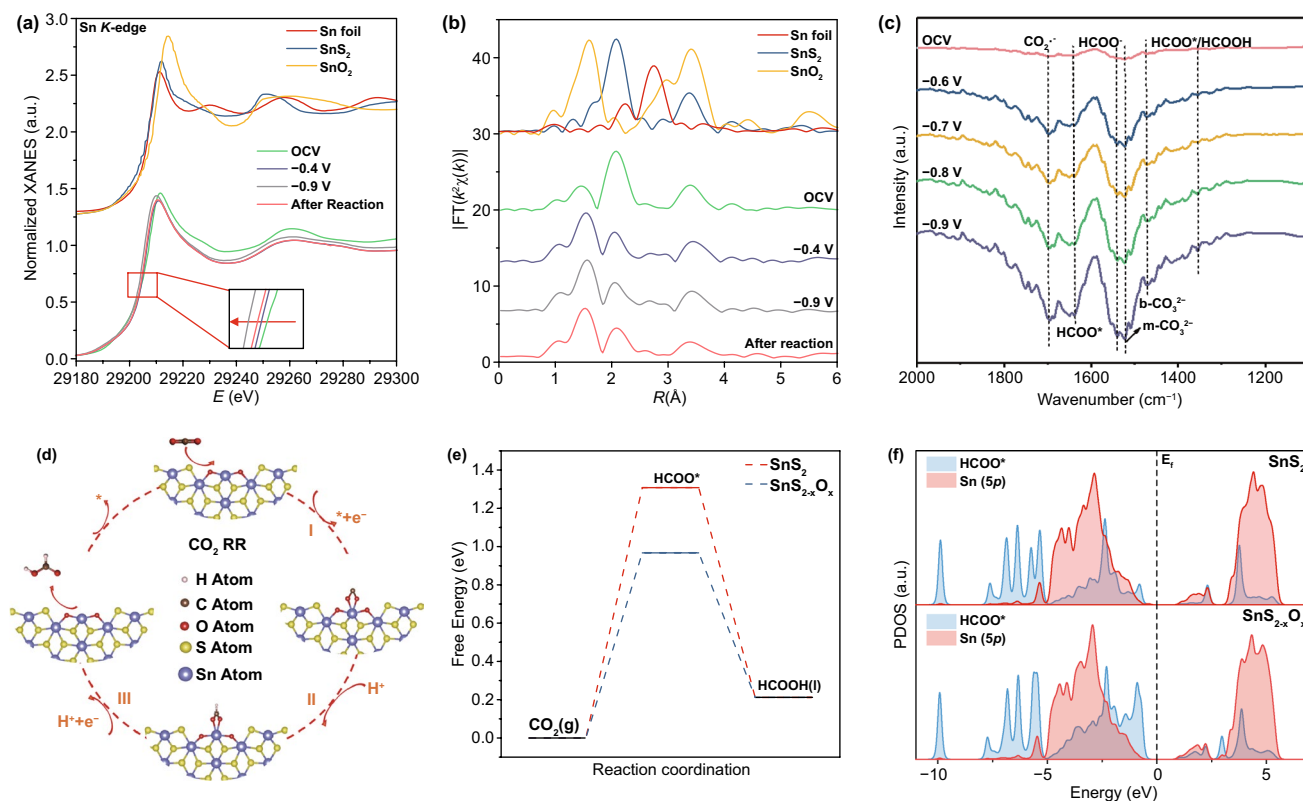



Fig. 4 **a** Operando XANES spectra at the Sn *K*-edge. **b** Operando k^2 -weighted FT spectra at the Sn *K*-edge. **c** Operando SR-FTIR spectra of the $\text{SnS}_{2-x}\text{O}_x/\text{CC}$ under the working condition. **d** Schematic of the whole CO_2RR mechanism on $\text{SnS}_{2-x}\text{O}_x$ nanosheets. **e** Gibbs free energy diagrams for CO_2 reduction to HCOOH on SnS_2 and $\text{SnS}_{2-x}\text{O}_x$ slabs. **f** Projected density of states (PDOS) of HCOO^* adsorbed on the SnS_2 and $\text{SnS}_{2-x}\text{O}_x$ slabs. The * represents an adsorption site

3.4 Operando Synchrotron Radiation Fourier Transform Infrared Spectroscopy Study

Operando synchrotron radiation Fourier transform infrared spectroscopy (SR-FT-IR) was further employed to investigate the catalytic mechanism for the well-designed $\text{SnS}_{2-x}\text{O}_x/\text{CC}$ during the CO_2RR . All SR-FTIR spectra were recorded with the electrocatalysts at CO_2RR catalytic process (open circuit, -0.6 , -0.7 , -0.8 , and -0.9 V) to reveal the production and transformation of key intermediates. As displayed in Fig. 4c, the monodentate carbonate groups (m-CO_3^{2-}) appeared at the peaks of ~ 1520 cm^{-1} , demonstrating that more CO_2 was adsorbed on the surface of electrocatalyst with the decrease in applied voltage. Meanwhile, a new characteristic peak appeared in the SR-FTIR spectra of ~ 1694 cm^{-1} ($\text{CO}_2^{\cdot-}$ radicals) and the intensity of peak continually increased as the applied potentials decreased,

indicating that the CO_2 molecules adsorbed on the catalyst surface were activated to $\text{CO}_2^{\cdot-}$ radicals during the reaction [42]. Meanwhile, as the cathode potential decreases, the peak intensity at ~ 1541 cm^{-1} (HCOO^-) increased further confirming the excellent proton trapping ability of $\text{CO}_2^{\cdot-}$ radicals [33]. The peaks at ~ 1354 cm^{-1} and ~ 1660 cm^{-1} is ascribed to the symmetry vibration of the HCOO^* intermediates, which corresponds to the key intermediates or the products for CO_2 electroreduction [43]. Based on the above-mentioned operando SR-FTIR analysis, the pathway of electroreduction from CO_2 -to- HCOOH conversion by the $\text{SnS}_{2-x}\text{O}_x/\text{CC}$ could be proposed as the following reactions (Fig. 4d):





3.5 Density Functional Theory (DFT) Calculations

DFT calculations were employed to elucidate the catalytic contribution from partial oxidation at $\text{SnS}_{2-x}\text{O}_x$ for CO_2RR . The models for pristine SnS_2 and $\text{SnS}_{2-x}\text{O}_x$ were chosen for the simulation. Figure S22 shows optimized adsorption configurations of HCOO^* intermediates on the armchair edges of the pristine SnS_2 slab and $\text{SnS}_{2-x}\text{O}_x$ slab with distinguishable Sn–O distances, from the material [44]. Specifically, the Sn–O bond length ($d_{\text{Sn-O}}$) is 2.28 Å for SnS_2 , while the bond length $d_{\text{Sn-O}}$ for $\text{SnS}_{2-x}\text{O}_x$ is reduced to 2.24 Å, implying that the surface oxygen injection effectively enhances the binding to the HCOO^* intermediate. Besides, DFT calculations were further conducted on the Gibbs free energy (ΔG) with multiple elementary reaction steps over SnS_2 with/without oxygen injection. As exhibited in Fig. 4e, for both SnS_2 and $\text{SnS}_{2-x}\text{O}_x$, the formation of HCOO^* is further confirmed to be the rate-limiting step for formate, which is consistent with the results of Tafel slopes. For the $\text{SnS}_{2-x}\text{O}_x$ slab, the ΔG for HCOO^* formation (ΔG_{HCOO^*}) was calculated to be 0.97 eV, which is much lower than that for pristine SnS_2 slab (1.31 eV), indicating surface oxygen injection enhanced the activation of CO_2 and correspondingly facilitated the formation of HCOO^* . To gain an in-depth insight into the nature of surface oxygen doping enhancing the intrinsic activity of SnS_2 , we calculated the projected density of state of HCOO^* adsorbed SnS_2 and $\text{SnS}_{2-x}\text{O}_x$ (Fig. 4f). In the HCOO^* PDOS, the dominant features are that HCOO^* exhibits strong interaction with the valence band region of SnS_2 and $\text{SnS}_{2-x}\text{O}_x$, which leads to strong chemical adsorption. Notably, the state density of HCOO^* overlaps more with the orbital of Sn ($5p$) in $\text{SnS}_{2-x}\text{O}_x$ with regard to that in SnS_2 , and the higher occupied state of HCOO^* is near the Fermi level, indicating that HCOO^* has a stronger interaction with $\text{SnS}_{2-x}\text{O}_x$, which is consistent with the calculation result of ΔG_{HCOO^*} . Furthermore, the charge density differences calculations also show that more electrons gather around the adsorption site in $\text{SnS}_{2-x}\text{O}_x$, indicating that the surface oxygen injection makes the SnS_2 edges exhibit a stronger affinity for HCOO^* species (Fig. S23). The above results confirm that surface oxygen injection alters the local electronic structure of Sn atom with optimal ΔG_{HCOO^*} to effectively facilitate the production of formate over CO_2RR .

Particularly, the above theoretical calculation results are consistent with the previous experimental results.

4 Conclusions

In conclusion, we developed SnS_2 nanosheets with surface oxygen modification for CO_2 electroreduction to formate and syngas (CO and H_2). The surface oxygen-injection engineering achieved exposure of Sn active site and optimal Sn electronic states, thereby enhancing the adsorption and activation of CO_2 . Surface oxygen injection on SnS_2 nanosheets significantly improved electrocatalytic activity and selectivity of CO_2 reduction to formate and syngas (CO and H_2). Specifically, at -0.9 V vs RHE, the $\text{SnS}_{2-x}\text{O}_x/\text{CC}$ exhibits the highest FE of 91.6% for carbonaceous products, including the FE of 83.2% for formate production and the FE of 16.5% for syngas with the H_2/CO ratio of 1:1. Moreover, the as-prepared $\text{SnS}_{2-x}\text{O}_x/\text{CC}$ displays an excellent durability for 10-h potentiostatic test with less than 4% decay in current density. *Operando* XAS unravels that the in situ surface oxygen doping into the matrix under working conditions effectively modulates the Sn local electronic state. *Operando* SR-FTIR and DFT calculations reveal that the surface oxygen doping enhanced the affinity for HCOO^* species by manipulating the Sn electronic states and accelerated the CO_2 activation. This work opens a span-new door for the design of advanced catalysts for CO_2 electroreduction.

Acknowledgements This work was supported by National Natural Science Foundation of China (Grants No. 12025505), China Ministry of Science and Technology (2017YFA0208300), Youth Innovation Promotion Association CAS (CX2310007007 and CX2310000091), and Open Fund Project of State Key Laboratory of Environmentally Friendly Energy Materials (20kfhg08). We would thank NSRL and SSRF for the synchrotron beam time. The calculations were performed on the supercomputing system in the Supercomputing Center of University of Science and Technology of China.

Author Contributions TC, TY, and WZ developed the idea and designed experiments. TC, XS, WZ, LW, and TD performed the catalyst synthesis and characterizations and FTIR measurements and electrochemical experiments. LC and TD performed the TEM characterization. WZ and XL made the XAFS calculation and analysis on Sn K -edge. TC and TY co-wrote the paper. TL and QL performed the DFT calculations. All authors discussed the results and commented on the manuscript.

Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by/4.0/>.

Supplementary Information The online version contains supplementary material available at <https://doi.org/10.1007/s40820-021-00703-6>.

References

1. H. Li, C. Qiu, S. Ren, Q. Dong, S. Zhang et al., Na⁺-gated water-conducting nanochannels for boosting CO₂ conversion to liquid fuels. *Science* **367**(6478), 667–671 (2020). <https://doi.org/10.1126/science.aaz6053>
2. J. Gu, C-S. Hsu, L. Bai, H.M. Chen, X. Hu, Atomically dispersed Fe³⁺ sites catalyze efficient CO₂ electroreduction to CO. *Science* **364**(6445), 1091–1094 (2019). <https://doi.org/10.1126/science.aaw7515>
3. T. Möller, F. Scholten, T.N. Thanh, I. Sinev, J. Timoshenko et al., Electrocatalytic CO₂ reduction on cuox nanocubes: tracking the evolution of chemical state, geometric structure, and catalytic selectivity using operando spectroscopy. *Angew. Chem. Int. Ed.* **132**(41), 18130–18139 (2020). <https://doi.org/10.1002/anie.202007136>
4. K. Jiang, Y. Huang, G. Zeng, F.M. Toma, W.A. Goddard et al., Effects of surface roughness on the electrochemical reduction of CO₂ over Cu. *ACS Energy Lett.* **5**(4), 1206–1214 (2020). <https://doi.org/10.1021/acsenenergylett.0c00482>
5. W. Ma, S. Xie, T. Liu, Q. Fan, J. Ye et al., Electrocatalytic reduction of CO₂ to ethylene and ethanol through hydrogen-assisted C-C coupling over fluorine-modified copper. *Nat. Catal.* **3**(6), 478–487 (2020). <https://doi.org/10.1038/s41929-020-0450-0>
6. Q. Gong, P. Ding, M. Xu, X. Zhu, M. Wang et al., Structural defects on converted bismuth oxide nanotubes enable highly active electrocatalysis of carbon dioxide reduction. *Nat. Commun.* **10**(1), 2807 (2019). <https://doi.org/10.1038/s41467-019-10819-4>
7. G. Wen, D.U. Lee, B. Ren, F.M. Hassan, G. Jiang et al., Orbital interactions in Bi-Sn bimetallic electrocatalysts for highly selective electrochemical CO₂ reduction toward formate production. *Adv. Energy Mater.* **8**(31), 1802427 (2018). <https://doi.org/10.1002/aenm.201802427>
8. X. Wei, Y. Li, L. Chen, J. Shi, Formic acid electro-synthesis by concurrent cathodic CO₂ reduction and anodic CH₃OH oxidation. *Angew. Chem. Int. Ed.* **60**(6), 3148–3155 (2021). <https://doi.org/10.1002/anie.202012066>
9. Y. Xing, X. Kong, X. Guo, Y. Liu, Q. Li et al., Bi@Sn core-shell structure with compressive strain boosts the electroreduction of CO₂ into formic acid. *Adv. Sci.* **7**(22), 1902989 (2020). <https://doi.org/10.1002/advs.201902989>
10. F. Li, L. Chen, M. Xue, T. Williams, Y. Zhang et al., Towards a better Sn: Efficient electrocatalytic reduction of CO₂ to formate by Sn/SnS₂ derived from SnS₂ nanosheets. *Nano Energy* **31**, 270–277 (2017). <https://doi.org/10.1016/j.nanoen.2016.11.004>
11. J. Xu, S. Lai, M. Hu, S. Ge, R. Xie et al., Semimetal 1H-SnS₂ enables high-efficiency electroreduction of CO₂ to CO. *Small Methods* **4**(10), 2000567 (2020). <https://doi.org/10.1002/smtd.202000567>
12. X. Li, S. Dou, J. Wang, X., Investigation of structural evolution of SnO₂ nanosheets towards electrocatalytic CO₂ reduction. *Chem. Asian J.* **15**, 1558–1561 (2020). <https://doi.org/10.1002/asia.202000252>
13. X. Zheng, P. De Luna, F.P. García de Arquer, B. Zhang, N. Becknell et al., Sulfur-modulated tin sites enable highly selective electrochemical reduction of CO₂ to formate. *Joule* **1**(4), 794–805 (2017). <https://doi.org/10.1016/j.joule.2017.09.014>
14. Z. Li, A. Cao, Q. Zheng, Y. Fu, T. Wang et al., Elucidation of the synergistic effect of dopants and vacancies on promoted selectivity for CO₂ electroreduction to formate. *Adv. Mater.* **33**(2), 2005113 (2021). <https://doi.org/10.1002/adma.202005113>
15. J. Wang, S. Ning, M. Luo, D. Xiang, W. Chen et al., In-Sn alloy core-shell nanoparticles: In-doped SnO₂ shell enables high stability and activity towards selective formate production from electrochemical reduction of CO₂. *Appl. Catal. B: Environ.* **288**, 119979 (2021). <https://doi.org/10.1016/j.apcatb.2021.119979>
16. J. Wu, Y. Xie, S. Du, Z. Ren, P. Yu et al., Heterophase engineering of SnO₂/Sn₃O₄ drives enhanced carbon dioxide electrocatalytic reduction to formic acid. *Sci. China Mater.* **63**(11), 2314–2324 (2020). <https://doi.org/10.1007/s40843-020-1361-3>
17. C. Hu, L. Zhang, L. Li, W. Zhu, W. Deng et al., Theory assisted design of n-doped tin oxides for enhanced electrochemical CO₂ activation and reduction. *Sci. China Mater.* **62**(8), 1030–1036 (2019). <https://doi.org/10.1007/s11426-019-9474-0>
18. W. Zhang, P. He, C. Wang, T. Ding, T. Chen et al., Operando evidence of Cu⁺ stabilization via a single-atom modifier for CO₂ electroreduction. *J. Mater. Chem. A* **8**(48), 25970–25977 (2020). <https://doi.org/10.1039/D0TA08369K>
19. W. Guo, X. Tan, J. Bi, L. Xu, D. Yang et al., Atomic indium catalysts for switching CO₂ electroreduction products from formate to CO. *J. Am. Chem. Soc.* **143**(18), 6877–6885 (2021). <https://doi.org/10.1021/jacs.1c00151>
20. I. Grigioni, L.K. Sagar, Y.C. Li, G. Lee, Y. Yan et al., CO₂ electroreduction to formate at a partial current density of 930 mA cm⁻² with in-p colloidal quantum dot derived catalysts.

- ACS Energy Lett. **6**(1), 79–84 (2021). (<https://doi.org/10.1021/acsenergylett.0c02165>)
21. R. Pang, P. Tian, H. Jiang, M. Zhu, X. Su et al., Tracking structural evolution: Operando regenerative CeO_x/Bi interface structure for high-performance CO₂ electroreduction. *Nat. Sci. Rev. nwaal87* (2020). <https://doi.org/10.1093/nsr/nwaa187>
 22. F. Yang, X. Ma, W.-B. Cai, P. Song, W. Xu, Nature of oxygen-containing groups on carbon for high-efficiency electrocatalytic CO₂ reduction reaction. *J. Am. Chem. Soc.* **141**(51), 20451–20459 (2019). <https://doi.org/10.1021/jacs.9b11123>
 23. H. Li, N. Xiao, Y. Wang, C. Li, X. Ye et al., Nitrogen-doped tubular carbon foam electrodes for efficient electroreduction of CO₂ to syngas with potential-independent CO/H₂ ratios. *J. Mater. Chem. A* **7**(32), 18852–18860 (2019). <https://doi.org/10.1039/C9TA05904K>
 24. R. Daiyan, E.C. Lovell, B. Huang, M. Zubair, J. Leverett et al., Uncovering atomic-scale stability and reactivity in engineered zinc oxide electrocatalysts for controllable syngas production. *Adv. Energy Mater.* **10**(28), 2001381 (2020). <https://doi.org/10.1002/aenm.202001381>
 25. X. Wang, Z. Wang, F.P. Garcia de Arquer, C.-T. Dinh, A. Ozden et al., Efficient electrically powered CO₂-to-ethanol via suppression of deoxygenation. *Nat. Energy* **5**(6), 478–486 (2020). <https://doi.org/10.1038/s41560-020-0607-8>
 26. M.S. Xie, B.Y. Xia, Y. Li, Y. Yan, Y. Yang et al., Amino acid modified copper electrodes for the enhanced selective electroreduction of carbon dioxide towards hydrocarbons. *Energy Environ. Sci.* **9**(5), 1687–1695 (2016). <https://doi.org/10.1039/C5EE03694A>
 27. J. Jeong, J.S. Kang, H. Shin, S.H. Lee, J. Jang et al., Self-supported mesoscopic tin oxide nanofilms for electrocatalytic reduction of carbon dioxide to formate. *Chem. Commun.* **57**(28), 3445–3448 (2021). <https://doi.org/10.1039/D1CC00927C>
 28. S. Gao, Y. Lin, X. Jiao, Y. Sun, Q. Luo et al., Partially oxidized atomic cobalt layers for carbon dioxide electroreduction to liquid fuel. *Nature* **529**(7584), 68–71 (2016). <https://doi.org/10.1038/nature16455>
 29. D.H. Won, C.H. Choi, J. Chung, M.W. Chung, E.-H. Kim et al., Rational design of a hierarchical tin dendrite electrode for efficient electrochemical reduction of CO₂. *CheSusChem* **8**(18), 3092–3098 (2015). <https://doi.org/10.1002/cssc.20150694>
 30. Y. Wang, Y. Wu, X. Liu, H. Zhang, M. Zhou et al., Atomic sandwiched p-n homojunctions. *Angew. Chem. Int. Ed.* **60**, 3487 (2020). <https://doi.org/10.1002/anie.202012734>
 31. A. Zhang, R. He, H. Li, Y. Chen, T. Kong et al., Nickel doping in atomically thin tin disulfide nanosheets enables highly efficient CO₂ reduction. *Angew. Chem. Int. Ed.* **130**(34), 11120–11124 (2018). <https://doi.org/10.1002/ange.201806043>
 32. M.F. Baruch, J.E. Pander III, J.L. White, A.B. Bocarsly, Mechanistic insights into the reduction of CO₂ on tin electrodes using in situ ATR-IR spectroscopy. *ACS Catal.* **5**(5), 3148–3156 (2015). <https://doi.org/10.1021/acscatal.5b00402>
 33. H. Cheng, S. Liu, J. Zhang, T. Zhou, N. Zhang et al., Surface nitrogen-injection engineering for high formation rate of CO₂ reduction to formate. *Nano Lett.* **20**(8), 6097–6103 (2020). <https://doi.org/10.1021/acs.nanolett.0c02144>
 34. Z. Zhang, F. Ahmad, W. Zhao, W. Yan, W. Zhang et al., Enhanced electrocatalytic reduction of CO₂ via chemical coupling between indium oxide and reduced graphene oxide. *Nano Lett.* **19**(6), 4029–4034 (2019). <https://doi.org/10.1021/acs.nanolett.9b01393>
 35. A. Zhang, Y. Liang, H. Li, X. Zhao, Y. Chen et al., Harmonizing the electronic structures of the adsorbate and catalysts for efficient CO₂ reduction. *Nano Lett.* **19**(9), 6547–6553 (2019). <https://doi.org/10.1021/acs.nanolett.9b02782>
 36. Z. Chen, M.-R. Gao, N. Duan, J. Zhang, Y.-Q. Zhang et al., Tuning adsorption strength of CO₂ and its intermediates on tin oxide-based electrocatalyst for efficient CO₂ reduction towards carbonaceous products. *Appl. Catal. B: Environ.* **277**, 119252 (2020). <https://doi.org/10.1016/j.apcatb.2020.119252>
 37. K. Fan, H. Zou, Y. Lu, H. Chen, F. Li et al., Direct observation of structural evolution of metal chalcogenide in electrocatalytic water oxidation. *ACS Nano* **12**(12), 12369–12379 (2018). <https://doi.org/10.1021/acs.nano.8b06312>
 38. S. Jin, Are metal chalcogenides, nitrides, and phosphides oxygen evolution catalysts or bifunctional catalysts? *ACS Energy Lett.* **2**(8), 1937–1938 (2017). <https://doi.org/10.1021/acsenergylett.7b00679>
 39. A. Dutta, A.K. Samantara, S.K. Dutta, B.K. Jena, N. Pradhan, Surface-oxidized dicobalt phosphide nanoneedles as a nonprecious, durable, and efficient oer catalyst. *ACS Energy Lett.* **1**(1), 169–174 (2016). <https://doi.org/10.1021/acsenergylett.6b00144>
 40. A. Sivanantham, P. Ganesan, A. Vinu, S. Shanmugam, Surface activation and reconstruction of non-oxide-based catalysts through in situ electrochemical tuning for oxygen evolution reactions in alkaline media. *ACS Catal.* **10**(1), 463–493 (2020). <https://doi.org/10.1021/acscatal.9b04216>
 41. O. Mabayoje, A. Shoola, B.R. Wygant, C.B. Mullins, The role of anions in metal chalcogenide oxygen evolution catalysis: electrodeposited thin films of nickel sulfide as “pre-catalysts”. *ACS Energy Lett.* **1**(1), 195–201 (2016). <https://doi.org/10.1021/acsenergylett.6b00084>
 42. L. Liu, Y. Jiang, H. Zhao, J. Chen, J. Cheng et al., Engineering coexposed {001} and {101} facets in oxygen-deficient TiO₂ nanocrystals for enhanced CO₂ photoreduction under visible light. *ACS Catal.* **6**(2), 1097–1108 (2016). <https://doi.org/10.1021/acscatal.5b02098>
 43. W. Zhang, Y. Hu, L. Ma, G. Zhu, Y. Wang et al., Progress and perspective of electrocatalytic CO₂ reduction for renewable carbonaceous fuels and chemicals. *Adv. Sci.* **5**(1), 1700275 (2018). <https://doi.org/10.1002/advs.201700275>
 44. H. Yang, Y. Hu, J. Chen, M.S. Balogun, P. Fang et al., Intermediates adsorption engineering of CO₂ electroreduction reaction in highly selective heterostructure Cu-based electrocatalysts for CO production. *Adv. Energy Mater.* **9**(27), 1901396 (2019). <https://doi.org/10.1002/aenm.201901396>